

Müller-BBM GmbH  
Robert-Koch-Str. 11  
82152 Planegg bei München

Telephone +49(89)85602 0  
Telefax +49(89)85602 111

www.MuellerBBM.com

Dipl.-Ing. (FH) Eva Müller  
Telephone +49(89)85602 3206  
Eva.Mueller@mbbm.com

2015-03-03  
M104146/20 MRE/KRR

## **Fabric „RUNNER“ Manufacturer Gabriel A/S**

**Determination of the  
airflow resistance according to EN 29053**

**Test Report No. M104146/20**

Client:	Gabriel A/S Hjulgagervej 55 9000 Aalborg Denmark
Consultant:	Dipl.-Ing. (FH) Eva Müller
Date of report:	2015-03-03
Delivery date of test objects:	2015-01-28
Date of test:	2015-02-09
Total number of pages:	In total 9 pages: 4 pages text, 3 pages Appendix A and 2 pages Appendix B.

Certified quality management system according to ISO 9001  
Accredited testing laboratory according to ISO/IEC 17025

Müller-BBM GmbH  
HRB Munich 86143  
VAT Reg. No. DE812167190

Managing directors:  
Joachim Bittner, Walter Grotz,  
Dr. Carl-Christian Hantschk, Stefan Schierer,  
Elmar Schröder, Norbert Suritsch

**Table of contents**

<b>1</b>	<b>Task</b>	<b>3</b>
<b>2</b>	<b>Basics</b>	<b>3</b>
<b>3</b>	<b>Test objects</b>	<b>3</b>
<b>4</b>	<b>Execution of measurements</b>	<b>3</b>
<b>5</b>	<b>Measurement results</b>	<b>4</b>
<b>6</b>	<b>Remarks</b>	<b>4</b>

Appendix A: Measurement results and evaluation

Appendix B: List of test equipment

## 1 Task

On behalf of Gabriel A/S, DK – 9000 Aalborg, the airflow resistance of three samples of the fabric type “RUNNER” was to be determined according to EN 29053 [1].

## 2 Basics

This test report is based on the following document:

- [1] EN 29053: Acoustics – Materials for acoustical applications – Determination of airflow resistance. 1993

## 3 Test objects

The tested fabric is described in table 1. The indicated characteristic values were determined by the testing laboratory on the basis of the sample.

Table 1. Test object.

Test object (manufacturer's information)	Area specific mass $m'$ [g/m <sup>2</sup> ]	Thickness $d$ [mm]	Appendix A, page
Sample 1: fabric type “RUNNER”, manufacturer Gabriel A/S material: 100 % polyester	295	2.8	1
Sample 2: fabric type “RUNNER”, manufacturer Gabriel A/S material: 100 % polyester	297	2.85	2
Sample 3: fabric type “RUNNER”, manufacturer Gabriel A/S material: 100 % polyester	294	2.8	3

## 4 Execution of measurements

The airflow resistance was determined according to EN 29053 [1].

The test method, the test facility and the test equipment used are described in Appendix B.

## 5 Measurement results

For the tested fabric type "RUNNER" a specific airflow resistance of

$$R_s = 12 \text{ Pa} \cdot \text{s/m}$$

was determined.

The determined air flow resistances of each of the three samples are shown in table 2.

The measurement results are shown in diagrams and tables in the test certificate in Appendix A of this report.

Table 2. Determined airflow resistances of the fabric "RUNNER".

Test object	Airflow resistance $R_s$ [Pa · s/m]	Appendix A, page
Sample 1: fabric type "RUNNER"	11	1
Sample 2: fabric type "RUNNER"	12	2
Sample 3: fabric type "RUNNER"	12	3

## 6 Remarks

The test results exclusively relate to the investigated subjects and conditions described.



Dipl.-Ing (FH) Eva Müller



Dipl.-Ing. (FH) Dominik Reif

This test report may only be published, shown or copied as a whole, including its appendices. The publishing of excerpts is only possible with prior consent of Müller-BBM.



Durch die DAkKS Deutsche Akkreditierungsstelle GmbH  
nach DIN EN ISO/IEC 17025 akkreditiertes Prüflaboratorium.  
Die Akkreditierung gilt für die in der Urkunde aufgeführten Prüfverfahren.

# EN 29053

## Determination of airflow resistance

**Client:** Gabriel A/S  
 Hjulmagervej 55  
 9000 Aalborg, Denmark

**Project No.:** M104146

**Mueller-BBM Probe No.:** 10078

**Test object:** fabric Runner, sample no. 01  
 colour: 60011  
 composition: 100 % polyester


Diameter: 100 mm  
 Thickness: 2.8 mm  
 Area-specific mass: 295 g/m<sup>2</sup>

Barometric pressure:  
 $B = 96,5 \text{ kPa}$

Temperature:  
 $\theta = 21,1 \text{ }^\circ\text{C}$

Relative humidity:  
 $r. h. = 18,3 \%$

$u/$ (mm/s)	$R_s/$ (Pa s/m)
1.95	11
3.39	10
4.85	11
6.30	10
7.74	11
9.20	11
10.65	10
12.10	10
13.54	10

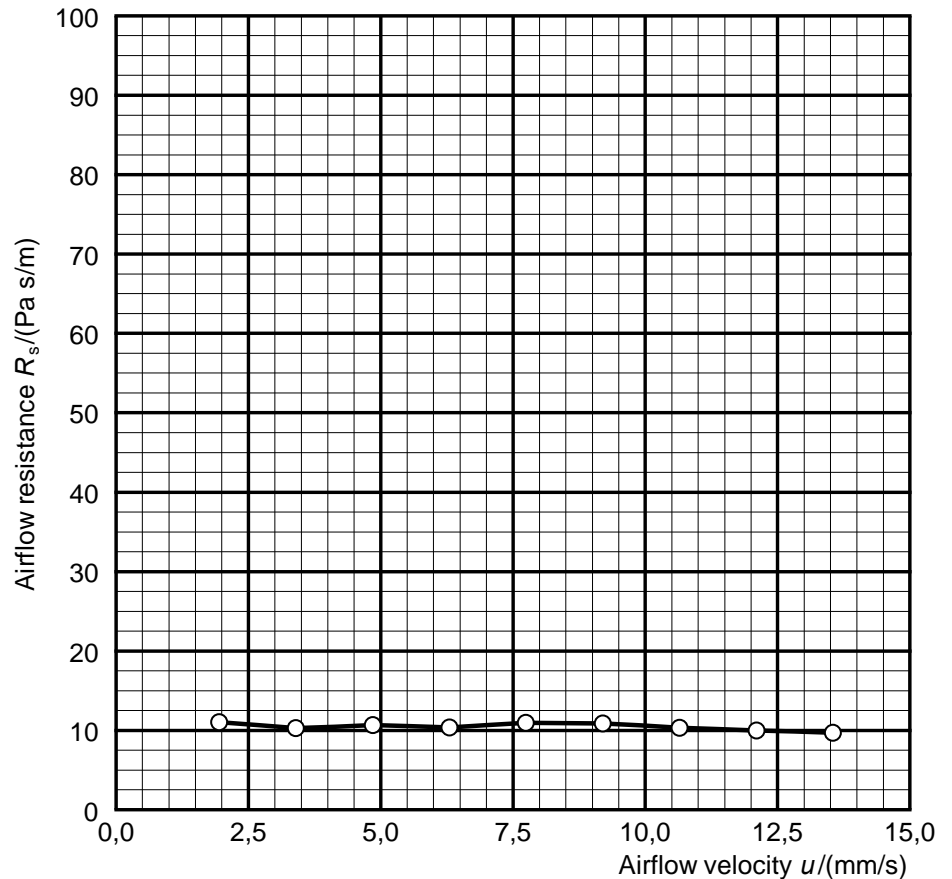

Airflow resistance  $R_s = 11 \text{ Pa s/m}$

# MÜLLER-BBM

Laboratory: Planegg  
 Responsible: Dipl.-Ing. (FH) Eva Müller  
 Date: 2015/03/03

# EN 29053

## Determination of airflow resistance

**Client:** Gabriel A/S  
Hjulmagervej 55  
9000 Aalborg, Denmark

**Project No.:** M104146

**Mueller-BBM Probe No.:** 10079

**Test object:** fabric Runner, sample no. 02  
colour: 60011  
composition: 100 % polyester


Diameter: 100 mm  
Thickness: 2.85 mm  
Area-specific mass: 297 g/m<sup>2</sup>

Barometric pressure:  
 $B = 96,5 \text{ kPa}$

Temperature:  
 $\theta = 21,6 \text{ °C}$

Relative humidity:  
*r. h.* = 15,9 %

$u/$ (mm/s)	$R_s/$ (Pa s/m)
0.50	11
1.95	12
3.40	11
4.86	11
6.31	10
7.76	11
9.22	10
10.67	10
12.11	9
13.56	9

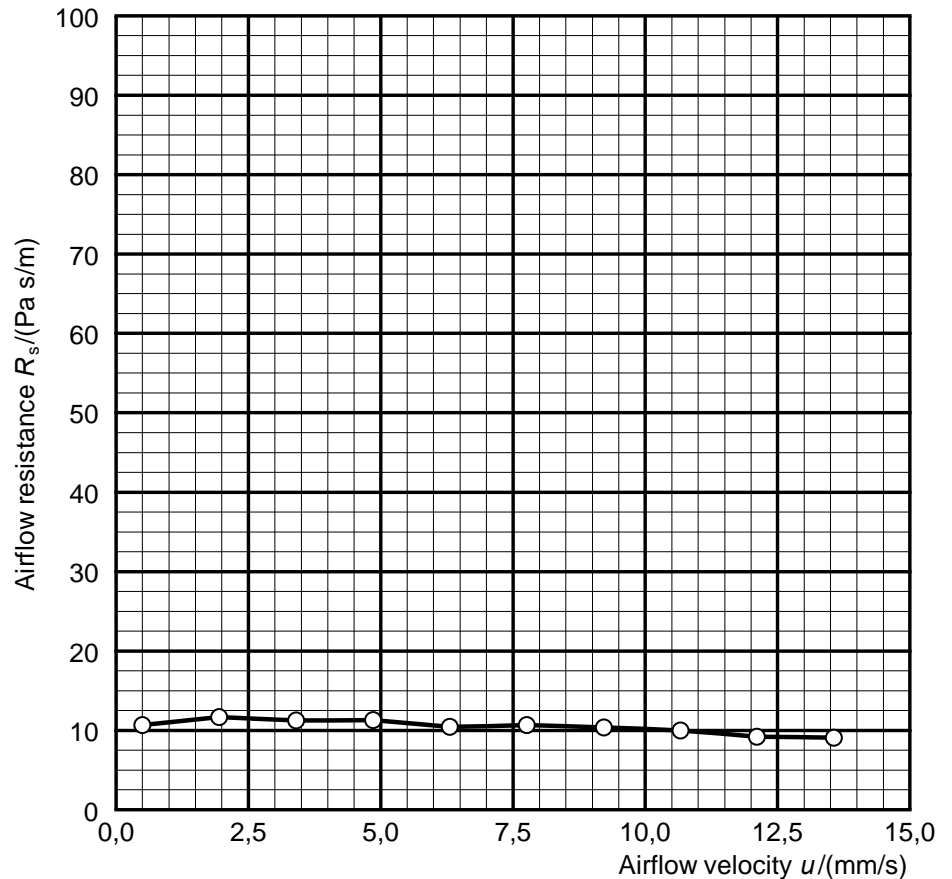

Airflow resistance  $R_s = 12 \text{ Pa s/m}$

# MÜLLER-BBM

Laboratory: Planegg  
Responsible: Dipl.-Ing. (FH) Eva Müller  
Date: 2015/03/03

# EN 29053

## Determination of airflow resistance

**Client:** Gabriel A/S  
 Hjulmagervej 55  
 9000 Aalborg, Denmark

**Project No.:** M104146

**Mueller-BBM Probe No.:** 10080

**Test object:** fabric Runner, sample no. 03  
 colour: 60011  
 composition: 100 % polyester


Diameter: 100 mm  
 Thickness: 2.8 mm  
 Area-specific mass: 294 g/m<sup>2</sup>

Barometric pressure:  
 $B = 96,5 \text{ kPa}$

Temperature:  
 $\theta = 21,9 \text{ }^\circ\text{C}$

Relative humidity:  
 $r. h. = 11,4 \%$

$u/$ (mm/s)	$R_s/$ (Pa s/m)
1.95	12
3.40	12
4.86	11
6.31	11
7.77	11
9.22	10
10.67	10
12.12	9
13.57	9

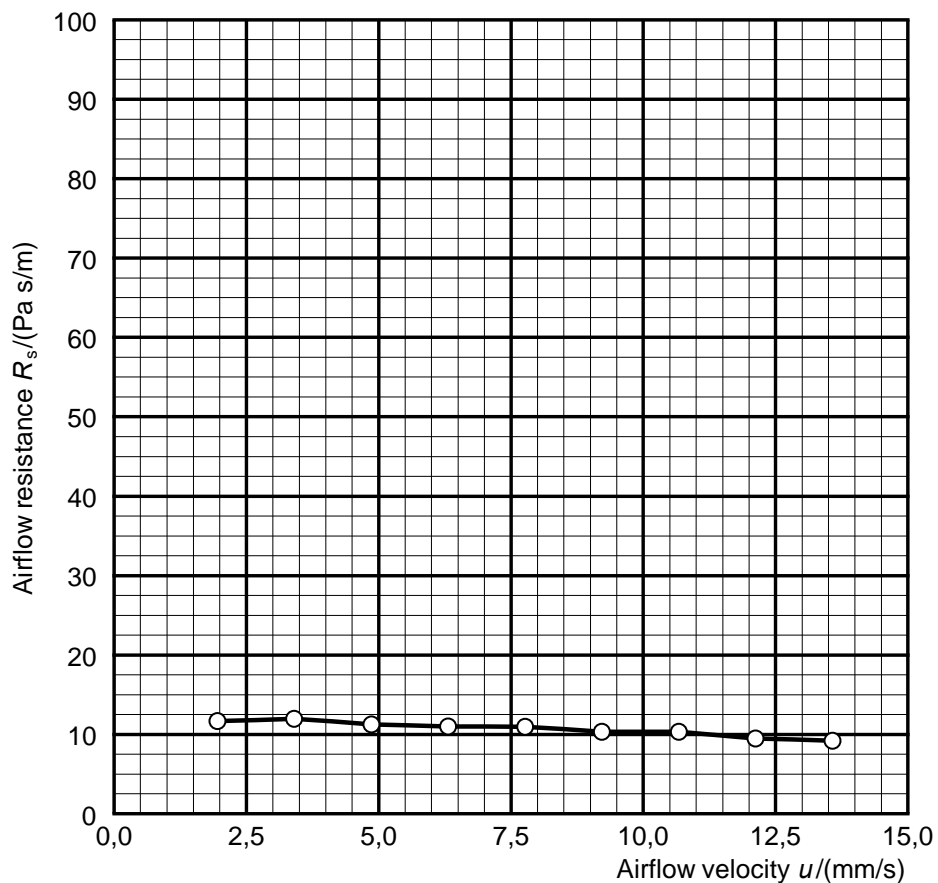

Airflow resistance  $R_s = 12 \text{ Pa s/m}$

# MÜLLER-BBM

Laboratory: Planegg  
 Responsible: Dipl.-Ing. (FH) Eva Müller  
 Date: 2015/03/03

## Description of the test procedure for the determination of the airflow resistance

### 1 Measurand

The specific airflow resistance  $R_S$  of the test object was determined. For this purpose the air pressure difference in front of as well as behind the test object was measured at different volumetric airflow rates. The specific airflow resistance  $R_{S,i}$  for each volumetric airflow rate  $q_i$  determined was calculated using the following equation:

$$R_{S,i} = \frac{\Delta p_i A}{q_i}$$

With

$R_{S,i}$  specific airflow resistance in Pa s/m;

$\Delta p_i$  air pressure difference across the test object with respect to the atmosphere in Pa;

$A$  cross-sectional area of the test object perpendicular to the direction of flow in m<sup>2</sup>;

$q_i$  volumetric airflow rate passing through the test object in m<sup>3</sup>/s;

$u_i$  linear airflow velocity in m/s;

In addition the linear airflow velocity  $u_i$  was determined:

$$u_i = \frac{q_i}{A}$$

The indicated measurement result is the specific airflow resistance  $R_S$ , which is calculated for an airflow velocity of  $u = 0.0005$  m/s by extrapolation with help of the linear regression.



## 2 Test procedure

The direct airflow method (method A according to EN 29053) was applied. A steady unidirectional airflow with different air flow rates is pressed through the test object in the specimen holder. The resulting pressure drop between the two free faces of the test object is measured.

The specimen holder had a diameter of  $D = 100$  mm.

## 3 List of test equipment

The test equipment used is listed in table B.1.

Table B.1. Test equipment.

Name	Manufacturer	Type	Serial-No.
Measurement system airflow resistance	Müller-BBM	M89319-00	315003
Software for measurement and evaluation	Müller-BBM	m ars	v1.0.0.2
Digital measuring slide	Mitutoyo	CD-15PPR	07019377
Electronic balance	Kern	440-49N	WC0633572